

# Change in torsion and strength of wires

Prakash Gawali\*, Amit Kumar Kundu

Acropolis Institute of Technology & Research, Indore, Madhya Pradesh, India

\*Corresponding Author

Received: 15 Jun 2024,

Receive in revised form: 11 Aug 2024,

Accepted: 17 Aug 2024,

Available online: 23 Aug 2024

©2024 The Author(s). Published by AI  
Publication. This is an open-access article  
under the CC BY license

(<https://creativecommons.org/licenses/by/4.0/>).

**Keywords—** Wire drawing, temperature,  
tensile strength, speed.

**Abstract—** The use of high speed in the wire drawing process become very common because of increase in customer demands and production rate. In this work the effect of high speed drawing (30m/sec) on mechanical and technological properties of high carbon steel wire has been investigated. Wire rod 5.50mm from steel grade 0.45% carbon and 0.56% carbon were drawn to 1.35mm in 13 draws and two speeds 10m/sec and 30m/sec. After each draw the following properties were determined; tensile strength ( $T_s$ ), temperature ( $T$ ), number of twists ( $N_t$ ), number of bends ( $N_b$ ). A large drop in the number of has been observed for final wires because of increased draw speed. However, there is also an advantage as the wire surface is much smoother after drawing at high speed than at low speed. The results were practically and statistically estimated.

## I. INTRODUCTION

In the wire drawing process, the cross section is reduced by the pulling it through a conical die which is inserted in the die box and the wire is pulled by cylindrical drum which is run by electric motor [1].

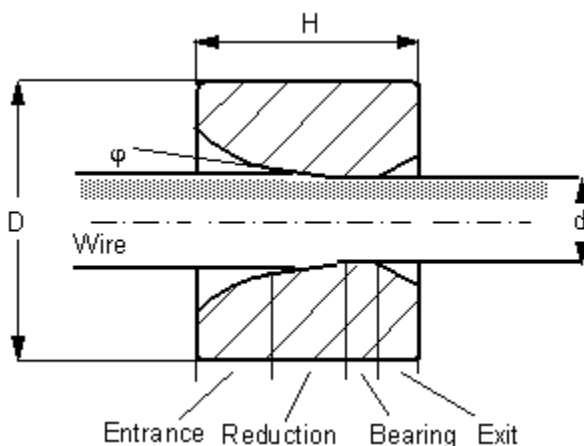


Fig. 1: Area reduction in wire drawing

The major variables in the drawing process are reduction in cross sectional area, die angle, friction along the die work piece interfaces and drawing speed. For successful drawing operation, careful selection of the

process parameters should be carried out. The drawing speed depends on wire material as well as reduction in area for high drawing speeds[2], the heat generated does not have sufficient time to dissipate and a substantial rise in the temperature [3, 4] occurs which has detrimental effect on the quality of product.

Wire drawing operations employing high area reduction and improved lubrication and friction conditions not only save energy, but also reduce production cost by avoiding intermediate passes and annealing operations [5].

Heat generation in wire drawing was first addressed by Siebel and Kobitzsch. [6]. An early refinement of this analysis was made by Korst.[7]. The approach is still widely used today in estimating the temperature rise in wire drawing. While the model predicts that the maximum temperature rise in wire varies with the square root of the drawing speed. It has been observed in experiments to vary linearly with the drawing speed[5]. As well as the cube root of the speed [8]. More recently, this temperature rise was observed to be independent of drawing speed.[9]

Intensifications of the drawing process can be achieved by an increase of a single and a total reduction or by an increase of a drawing speed. However, in practical, technical and economical advantages with a faster speed

are remarkable higher than during drawing with maximum reductions because a higher drawing speed increases the production yield for a specific drawing machine. There has been a trend in wire manufacturing to using high-speed multi hole drawing systems. This application is very important for further industry development but at the same time it is necessary to know the effect of this type of process of not only for the mechanical properties of the drawn wires, but also the factors such as die wear,

lubricant section, die cooling of the dies, drawing drums and others.

### Experimental procedure

The material used to the investigation was rise rod about diameter 5.50mm of low carbon steel after TRIP type heat treatment. The chemical composition of used steel in the investigation is presented in table 1.

Table 1: The chemical composition of TRIP steel

Mass contents in %								
C	Mn	Si	P	S	Cu	Ni	Mo	Sn
0.45	1.40	0.80	0.01	0.07	0.025	0.01	0.006	0.004
0.56	1.30	0.70	0.015	0.08	0.020	0.01	0.004	0.004

Table 2: The volumetric phase contain

Phase contain			
Ferrite, %	Bainite, %	Retained austenite +~Martensite <sup>1</sup> , %	Retained austenite <sup>2</sup> %
68.3	15.8	7.5	7.9

After heat treatment and metallographic investigation which confirmed used TRIP type structure, TRIP steel wires drawn in 13 drafts with different drawing speed from diameter 5.5mm to 1.35mm by using classical die with

sintered carbides about angle  $2\alpha = 12^\circ$ . In table 3, the main parameters of drawing process are shown, where: V – drawing speed, A – medium single draft, A<sub>t</sub> – total draft in percentage.

Table 3: The parameters of drawing process

Variant	Drawing machine	Carbon %	V, m/s	Drafts number	A%	At%
A	BB-8	C – 45	8	13	20	93.98
B	BB-8	C- 45	25	13	20	93.98
A	BB-8	C – 56	8	13	20	93.98
B	BB-8	C – 56	25	13	20	93.98

In order to estimate the influence of drawing speed on mechanical properties of wires with TRIP effect, described relation between tensile strength T<sub>s</sub>, Temperature T in °C uniform elongation in total draft function for wires drawn according to variant A (V= 8 m/s), B(V = 25m/s).

For better estimation of the influence of drawing speed on properties TRIP steel wires in the work, modeling of wire drawing process (in Drawing 2D program) has been carried out. It has been estimated:

temperatures, non-dilatation strain and internal stresses drawn wires. Used in program model multi passes drawing (with a few following after themselves single draft) allows to dissolve coastal task with the range of theory of temperature and tensile strength by the variation of the carbon and speed

Table 4: Schedule of draws and mean values of mechanical and technological properties of wires of steel C45. Draw speed 30m/s. and 10m/s.

V= 30m/s C 45									
L <sub>p</sub>	φ	A <sub>p</sub>	A <sub>t</sub>	T <sub>s</sub>	T	E <sub>l</sub>	C <sub>t</sub>	N <sub>b</sub>	N <sub>t</sub>
	(mm)	(%)	(%)	(MPa)	°C	(%)	(%)		
1.	5.50	0.0	-	793	-	8.7	43	14	13
2.	4.91	20	20	872	99	2.6	21	13	14
3.	1.80	20	89.29	1626	239	1.8	53.4	13	28
4.	1.63	20	91.22	1705	250	1.4	52.6	11	30
5.	1.49	20	92.68	1783	261	1.6	51	11	32
6.	1.35	20	93.98	1852	274	1.7	48	10	34
V= 10m/s C 45									
1.	5.50	0.0	-	793	-	8	44	14	13
2.	4.91	20	20	867	94	3	48	13	15
3.	1.80	20	89.29	1600	235	2	51	13	32
4.	1.63	20	91.22	1650	242	2.1	53	12	34
5.	1.49	20	92.68	1757	250	1.8	50	12	36
6.	1.35	20	93.98	1820	260	1.7	48	11	40

Table 5: Schedule of draws and mean values of mechanical and technological properties of wires of steel C71. Draw speed 25m/s. and 8m/s.

V= 30m/s C 56									
L <sub>p</sub>	φ	A <sub>p</sub>	A <sub>t</sub>	T <sub>s</sub>	T	E <sub>l</sub>	C <sub>t</sub>	N <sub>b</sub>	N <sub>t</sub>
	(mm)	(%)	(%)	(MPa)	°C	(%)	(%)		
1.	5.50	0.0	-	1038	-	8	46.8	13	12
2.	4.91	20	20	1117	114	2	19.7	12	13
3.	1.80	20	89.29	1871	253	1.8	53.5	12	26
4.	1.63	20	91.22	1950	254	1.5	51.8	11	28
5.	1.49	20	92.68	2018	264	1.6	51.4	10	30
6.	1.35	20	93.98	2097	276	1.7	47.3	9	32
V= 10m/s C 56.									
1.	5.50	0.0	-	1038	-	8.7	46.8	13	12
2.	4.91	20	20	1062	108	2.8	50.7	13	14
3.	1.80	20	89.29	1792	221	2.3	53.9	13	30
4.	1.63	20	91.22	1870	238	2.1	53.2	12	32
5.	1.49	20	92.68	1956	242	1.7	50.1	11	34
6.	1.35	20	93.98	1980	256	1.8	48.1	10	36

φ = Wire diameter in mm

A<sub>p</sub> = Area reduction per pass in %

A<sub>t</sub> = Total area reduction in %.

T<sub>s</sub> = Tensile strength, MPa.

T = Temp. rise in °C in each pass.



E<sub>l</sub> = Total elongation %.



C<sub>t</sub> = Total contraction%

**II. RESEARCH RESULTS: WIRE PROPERTIES**

The wire rod were examined at Tata steel plant for the following properties: tensile strength ( $T_s$ ) in MPa, total elongation ( $E_l$ ) in %, contraction ( $C_i$ ), number of twists  $N_t$ , Number of bends  $N_b$ . The mean values in the table were calculated for the mechanical properties of the 1.35mm wire drawn from the 5.5mm wire rod (steel C 45) at two draw speeds (10m/s and 30m/s). Table 5 shows the same values for the wire drawn from the 5.5mm wire rod (C-56) at draw speeds (10m/s to 30m/s).

The following parameters were calculated for each draw: average temperature on the cross section of the wire ( $T$ ), wire surface temperature ( $T_i$ ). Table 4 shows the value of calculated parameters for all draws with a speed 10m/s for steel C45 at a speed of 30m/s. Table 5 shows the value of  $A$ ,  $A_t$ ,  $T_s$ ,  $T$ ,  $N_b$ ,  $N_t$  for all draws for steel C56 at a speed of 10m/s and 30m/s in the final. The wire surface was observed with an optical microscope at the magnification of 400x.

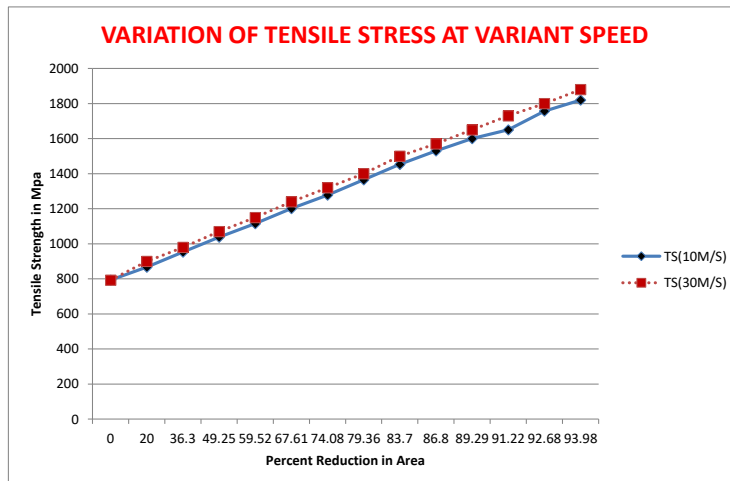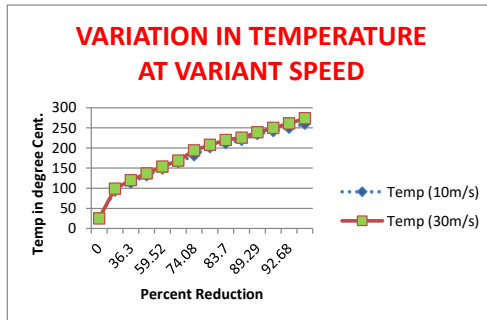

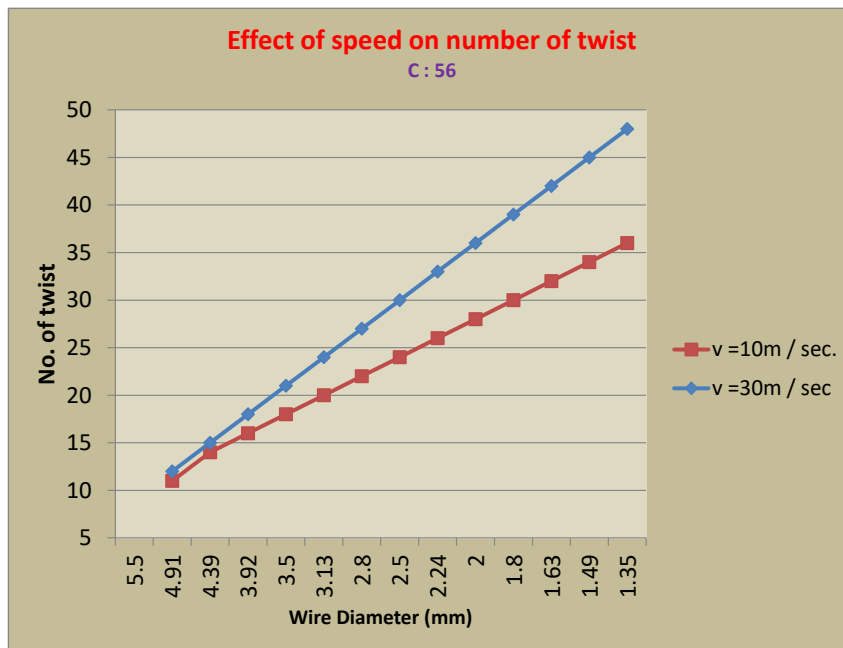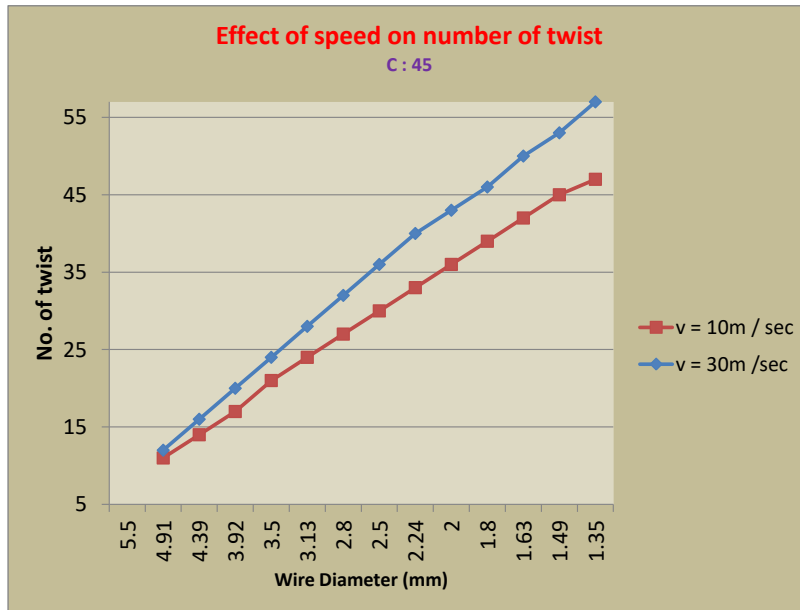

On the base of a preliminary analysis of data from tables 1-4 and others, it has been decided that process parameters and mechanical properties of tested wires will be estimated for all initial draws, three final draws and last one. This will be helpful in precisely estimating the effect of the draw speed on the above mentioned features of the process and wires ,it can be stated that value of draw stress component in the initial group of draws are independent of a draw speed( for given steel grade). Also that they increase for the final three draws and are highest for the

last draw. The calculated values of this draw stress component for test wires made from steel C45 are lower than those made from steel C56. A similar relationship can be seen for the frictional component of draw stress. In general, the contribution of the friction component in a draw stress is smaller than that for a deformation one.

Regarding the effect of draw speed on temperature of a wire surface, Table 4 and 5 shows that it is similar at a slow draw speed, 10m/s, for all three groups of analyzed draws for steel C45. The result, respectively

are: draws (1-10) 100 - 140°C, draws (11-12) 240 - 250°C and for last draw, 255- 260°C. Drawing at a speed of 30m/s for this same steel, the comparative surface temperatures are : draws (1-10) 100 - 240°C, draw (11-12) 260 - 265°C and for last draw 274 - 276°C. Drawing wires made from the C56 steel resulted in higher surface temperature than for all analyzed wires made from C45 steel, but also in this case for a draw speed of 10m/s the temperature goes on increasing as the carbon percentage increase for draw (1-10) the temperature rise is 10-15°C for draw (11-12) temperature rise is 4-8°C for last draw the temperature rise is 4°C. For a speed of 25m/sec for the considered group of draw the temperature rise for draw (1-10) is 15°C, for draw (11-12) temperature rise is 3-4°C, for last draw temperature rise is 2°C.

Regarding the effect of drawing speed on number of bends, Table 4 and Table 5 shows that the number of bends for draw (1-10) having same value, for draw (11-12) the number of bend decrease by 1, for last draw the number of bend decreased by 1. But as the carbon percentage increases from C45 to C56 the number of bends decreased by 1.

Regarding the effect of drawing speed on the torsion value, Table 4 and Table 5 shows that for C45 as the speed varies from 10m/sec to 30m/sec the torsion value for draw (1-5) increases by 1, for draws (6-13) increases by 2. And as the carbon increases from C46 to C71 the torsion value for draw (1-5) decreases by 1, for draw (6-13) decreases by 2.

Drawing speed was found to have a remarkable effect on tensile strength. The tensile strength in MPa initially having lower value but increases constantly from first pass to last pass. For carbon C – 45, from 793MPa to 1820MPa when the speed is 8m/sec, but tensile strength increases 793 to 1852MPa, when the speed is 30m/sec.

For C – 56 the tensile strength increases from first to last pass 1038MPa to 1870MPa, when speed is 8m/sec and tensile strength increases from 1038MPa to 2097MPa when the speed is 25m/sec.

Thus at high speed and high carbon the value increases by 5 to 10%.

### III. CONCLUSIONS

1. The increase of speed from 8m/sec to 25m/sec caused the increase of tensile strength about 5-6%.
2. The increase of speed causes rise in temperature, which is required to reduce to avoid strain hardening and wire breakage.

3. The increase in speed causes to reduce number of bends by 8-10%. and also as the carbon percentage increase the number of bends goes on decreasing.
4. Higher speed decreases the number of twists observed.
5. At higher speed it is observed that the surface of the wire is smoother than at lower speed.
6. At higher speed the number of bends decreases and it again decreases by increases in the carbon percentage

### REFERENCES

- [1] [http://en.wikipedia.org/wiki/Wire\\_drawing](http://en.wikipedia.org/wiki/Wire_drawing)
- [2] A.K.Lis, J. Lis, Effect of hot deformation and cooling rate on phase transformations in low carbon bainitic steel, proceeding of 11<sup>th</sup> international scientific Conference CAM3S'2005 "Contemporary Achievements in Mechanics, Manufacturing and Material Science" Gliwice – Zakopane 2005, (CD-ROM).
- [3] J.W. Pilaczyk, Z.Muskalski, B Golis, S. Wiewiorowska, M. Sliga, Influence of heat treatment of trip steel wire rod on structure and mechanical properties. Conference Proceedings "Global technologies for Emerging Market's", New Delhi, India 2006, 171-182.
- [4] M. Suliga, Z. Muskalski, the influence of single draft on mechanical-technological properties of TRIP steel wires, Metallurgist-news Metallurgist (2007) 353-356.
- [5] J.Adamezyk., A.Grajcar, heat treatment of TRIP- aided bainitic steel, proceeding of the 11<sup>th</sup> International scientific conference CAM3S'2005' Contemporary Achievements in Mechanics, Manufacturing and Materials Science, Gliwiczakopane2005(CD-ROM).
- [6] A.K. Lis, B.Gajda, Modeling of the DP and trip microstructure in the CMnAlSi automotive steel, Proceeding of the 11<sup>th</sup> International scientific conference CAM3S'2005 "Contemporary achievements in mechanics, manufacturing and the material science", Gliwice-Zakopane 2005, (CD-ROM).
- [7] A. Grajcar, Effect of hot working in the  $\gamma + \alpha$  range on a retained austenite fraction in TRIP- aided steel, journal of Achievements in Materials and Manufacturing Engineering 22/2 (2007) 79-82.
- [8] A. Gajda, A.K. Lis, Thermal processing of CMnAlSi steel at  $(\gamma+\alpha)$  temperature range, Journal of Achievements in Materials and Manufacturing Engineering 18(2006) 355-358.
- [9] P.J. Jacaues, A. Petein, P. Harlet, Improvement of mechanical properties through concurrent deformation and transformation: Newsteels for the 21<sup>st</sup> century, TRIP – International Conference on TRIP aided high strength Ferrous alloys, GRIPS-Proceeding, Ghent (2002) 281-286.